

WEAR OF STEEL AGAINST CARBON FIBRE REINFORCED PPS

Quintelier J.¹, Samyn P.¹, De Baets P.¹, Ost, W.¹, Van Paepegem, W.²

¹Laboratory Soete, subdivision Tribology and Fatigue, Ghent University, Belgium

²Laboratory Soete, Subdivision Mechanics of Materials and Structures, Ghent University, Belgium

Abstract:

Based on the well-known pin-on-disc test rig, a new test set-up has been developed for the online measurement of the wear and friction of steel sliding against polymer matrix composite. Instead of the standard composite specimen and steel disc, a rotating composite disc and steel pin are used. This new test set-up is used to investigate the wear and frictional behaviour of carbon fibre reinforced (Poly phenylene sulphide) PPS. The material used is a 5-harness satin weave carbon/PPS composite with a carbon content of 50 ± 3 %. The mating surface of the pin is the ball of a ball bearing, with a radius of 8 mm, and a well-known roughness. The frictional behaviour of this material pair results in a friction coefficient of 0.33, while a carbon film is formed in the wear track. This results in a lowering of the frictional behaviour. The wear rate is rather low, but when the wear track is covered with a carbon film suddenly the wear rate raises. This is not due to the wear of the composite material but only as a result of the start of terrible wear of the steel counter face. Moreover, the wear of the pin is strongly related to the wear track. The pin is flattened at the sides of the formed wear track, but in contact with the carbon film there is less wear, resulting in a pin with two flat sides, making contact with the original surface, and a rig in the middle of the pin following the roundness of the wear track. It can be stated that although the high contact pressure at the beginning resulted in plastic deformation of the PPS matrix, once a carbon film is formed the composite material is protected, resulting in the severe wear of the steel counter face

Keywords: Composites, Wear, Pin on disc, carbon film

1. INTRODUCTION

Since poly phenylene sulphide (PPS) (Fig. 1) is a semi-crystalline thermoplastic polymer with high glass transition temperature (90°C) and high melting temperature (280°C) and high mechanical strength, PPS is a promising rubbing material as reported by many authors [1-8].

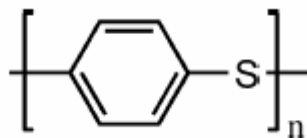


Fig. 1: Poly (p-phenylene sulphide)

In the case of pure PPS, the steady state wear rate increased at both low and high sliding speeds. Thermal softening was observed at the sliding speed of 2 m/s thereby resulting in higher wear rate. The coefficient of friction of PPS decreased as the sliding speed was decreased from 1.0 to 0.25 m/s, but the highest sliding speed of 2 m/s showed the lowest coefficient of friction because of thermal softening [9-10]. It was also shown that the development of a transfer film was associated with counter face roughness, and the transfer films were patchy and discontinuous when the counter face roughness was either very low or very high. EDS analysis of the transfer film of PPS composites with CuS as filler material showed that the transfer film consisted of FeS,

CuO, Cu, and Fe_xO_y . This indicated tribochemical reaction between Fe in the counterface and S in the filler. The indication of such a reaction was not found from EDS analysis of the transfer film of ZnF_2 -PPS composite [4]. In tribological testing the steel counterface does not wear due to the PPS, but as a result of the abrasive action of possible fillers.

In this paper it is shown that the wear resistance of the carbon fibres reinforced PPS, is depending on the behaviour of the carbon fibres.

The pin (7), made of steel, with a length of 35 mm is hollow at the top, because measuring bending of the pin with strain gauges requires a sufficient strain in the steel pin. Two flat parallel faces close to the contacting surface are places for an accelerometer (see Fig. 2,a) and an acoustic emission sensor. Thermocouples can be placed all over the pin geometry. A ball from a deep groove ball bearing forms the mating surface, or the top of the pin. Thus the pin can be reused, while only the ball has to be replaced.

Characteristics of this test rig are: relative velocities from 10 up to 100 mm/s, a possible

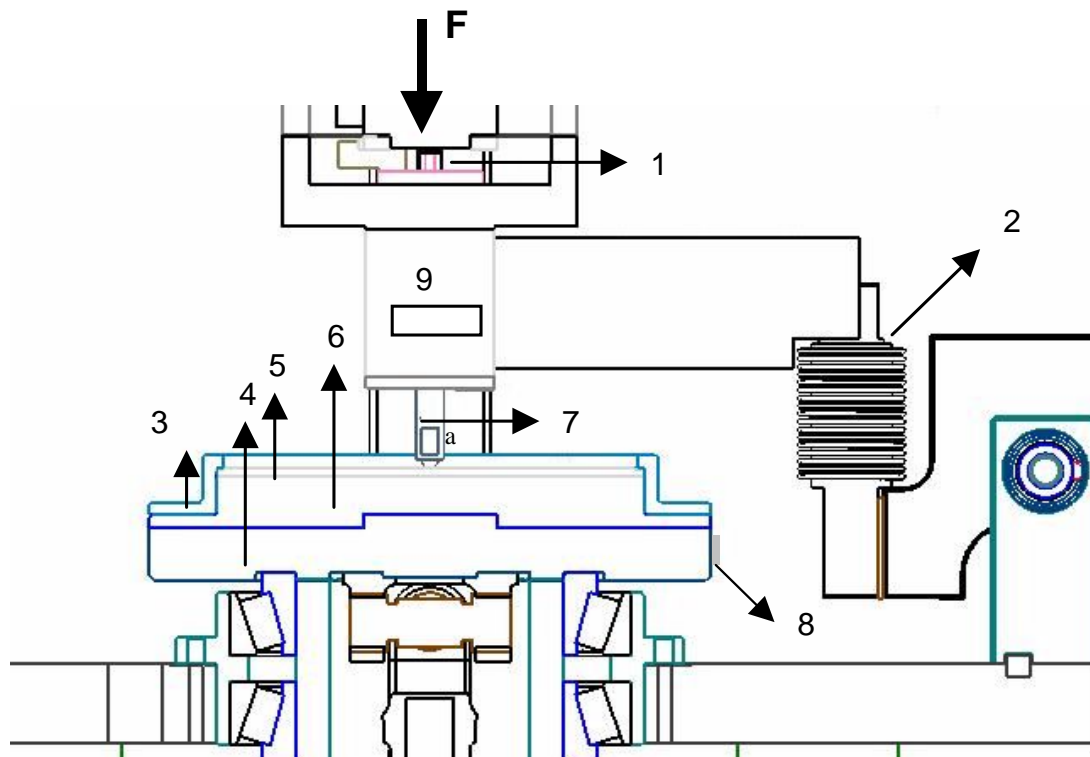


Fig. 2: Pin-on-disc test rig, with (1) normal load cell, (2) friction load cell, (3) ring for keeping the composite disc fixed and in the centre, (4) fixed disc on the test rig, (5) composite disc, (6) removable disc where the composite test specimen is glued on, (7) pin, (8) magnets for triggering, (9) contactless proximitor counter face

2. TEST RIG

A new pin-on-disc test rig (Fig. 2) was built in order to be able to monitor the tribological behaviour of composite materials as bearing material. The materials on the most common pin-on-disc set-up [11-14] (composite pin/steel disc) were switched, namely a composite disc and a steel pin were used. This yields the possibility that in one test the influence of the fibre orientation on wear and friction can be investigated by choosing an unidirectional fibre reinforced composite.

normal load up to 1000 N, and the possibility to place additional sensors on the pin (2) for further research.

For the measurement of the wear depth of the wear track, a contactless proximitor (9) is used, providing an estimate of the evolution of the wear depth with time.

For measuring the normal force on the pin a load cell is placed above the pin (1). This load cell is protected by a spring mechanism, which allows pressing directly on the load cell, without damaging this load cell. Another method to measure the normal force on the pin is by measuring the air pressure in the cylinder used

as supplier for the normal force. This cylinder is connected via valves to the compressor. The friction force is measured with a load cell (2).

On the rotating disc, magnets (8) are placed, which are used as trigger for the various signals, but are also used to synchronize measured friction and wear signals with the fibre orientation. This type of indication is very reliable, and gives the possibility to calculate the values of the friction force related to a specific orientation (0° , 90° , 180° , 270°).

On a steel disc (6), the composite disc (5) is fixed with bee wax. Due to high frictional loads

this might not prevent rotation of the disc, therefore the disc is kept in place with an external ring (3). This ring not only presses slightly the composite disc onto the steel disc at the edge, but also makes sure that the composite disc stays centered to the rotation, yielding a perfectly circular wear pattern on the disc. This replaceable disc construction is then placed on a fixed disc (4). The whole disc construction rests on two bearings, and is driven by the axis of a reduction unit, which itself is driven by an asynchronous motor through a speed reducer and a timing belt.



Fig. 3: Scanning electron microscopic image of the cross section of the carbon-fibre reinforced PPS

3. MATERIALS AND METHOD

The fibre-reinforced composite under study was a 5-harness satin (see Fig. 4) weave carbon/PPS composite. Poly phenylene sulphide (PPS) is a commonly used thermoplastic matrix in aeronautical applications. Eight layers of fabric were stacked in sequence $[0^\circ/90^\circ]_{2s}$, the angle indicates the warp direction of the reinforcement layer. This result in a carbon content of $50 \pm 3\%$. Discs were cut out by water jet process, and a cross section of the material is shown in fig 3. The white zones constitute pure PPS, while the dark zones represent carbon fibres.

The EDX-spectrum of this cross section (Fig. 5), shows high peaks of C (Carbon) and S

(Sulphur). Also Au (gold) is found in minor amounts. This is due to the fact that the sample was pre-treated with a minor amount of gold for higher contrast SEM images. The peaks of Si (Silicon) and K (Potassium) originate from the abrasives used in water jet cutting.

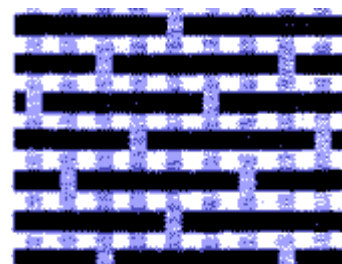


Fig. 4: Schematic diagram of 5-harness satin weave

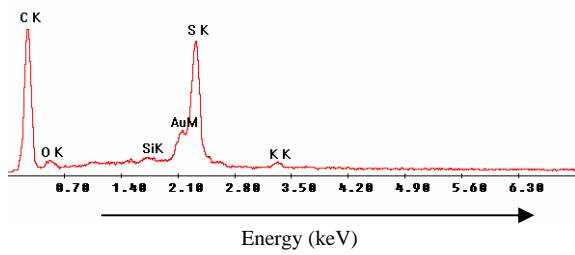


Fig. 5: EDX spectra of the area in fig 3.

Carbon fibre reinforced PPS-discs were mounted on the removable disc (fig 2, 6). A closer look on the test set up is given in Fig. 6. The test parameters were 250N normal load and a relative velocity of 20 mm/s. A test consisted of 10.000 revolutions with a sliding distance of 400 mm per revolution, yielding a total sliding distance of 4 km.

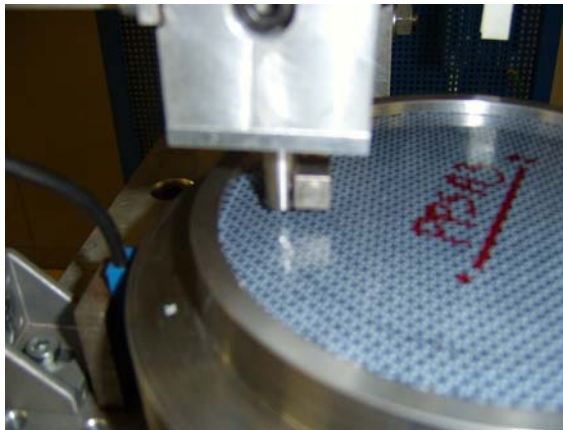


Fig. 6: Pin-disc configuration, closer look at contact zone

4. RESULTS

Results of the tests performed at 250 N and 20mm/s are presented in figs. 7 and 8. In these graphs, the wear and frictional behaviour of the pin-disc material combination is plotted as a function of the time. Each point of the curvature is obtained by averaging 250 points, measured at 50Hz of each round, so each curve in the graphs of Fig. 7 and Fig. 8 consists of 10.000 points.

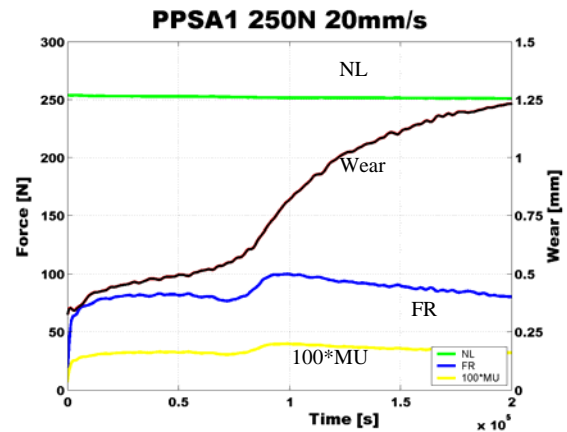


Fig. 7: Test results at 250N, 20mm/s (Disc PPSA1) with the upper line the normal load (NL, left axis), the 2 lowest lines are the friction force (FR, left axis) and the coefficient of friction multiplied by 100 (100*MU, left axis), also indicated on the left, while the second line from above is the evolution of the wear depth (right axis)

At a constant normal load (250N) the evolution of wear is rather exceptional. After a small running in period, the composite wears very slowly, until, at a certain moment (75.000 s), the wear depth increases very strongly. Just before the rise in wear rate, the friction force decreases, then rises when the wear rate rises, and lowers again linearly after 100.000 s. The total wear depth after testing is 0.95mm.

A second test (Fig. 8) performed under the same conditions shows an identical phenomenon, albeit somewhat later on in the test.

While in Fig. 7 the wear rate increases after 75.000 s, in Fig. 8 the increase of the wear rate starts after 115.000 s. The rest of the graph is exactly the same, as well in evolution in time as in magnitude.

Images of the disc were taken during testing and provide an overview of the worn disc (see Figs. 9 – 10).

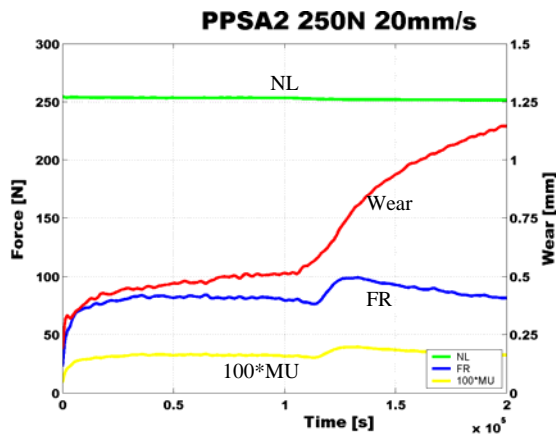


Fig. 8: Test results at 250N, 20mm/s (Disc PPSA2) with the upper line the normal load (NL, left axis), the 2 lowest lines are the friction force (FR, left axis) and the coefficient of friction multiplied by 100 (100* μ , left axis), also indicated on the left, while the second line from above is the evolution of the wear depth (right axis)

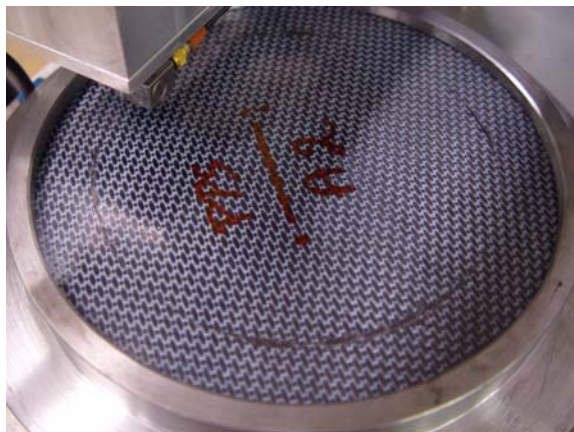


Fig. 9: Image of the wear state of disc PPSA2 after 450 rounds

Fig. 9 shows the wear track of the disc after 450 rounds. As fig 9 shows, the width of the wear track on the disc correlates with the fibre orientation. The 0° (parallel fibre orientation relative to the direction of motion) and the 90° (indicated via the line in the middle of the disc) orientation have an earlier wear through the top layer of PPS than the 45° , and perpendicular (90°) orientation has an earlier wear through than the parallel (0°) as shown by the larger wear track at the 90° orientation.

At the end of the test (Fig. 10) wear debris can be seen next to the wear track, almost equally divided between the inner diameter and the outer diameter of the wear track. Interesting to note is that between the two edges with wear debris, two flat zones are visible where carbon fibres and PPS (as in the original top view of the

disc) can be seen, while in the middle between the wear debris wear track can be seen. These two flat zones does not seem to have suffered from any wear (original surface), while in the middle of the wear track, a carbon (black) film is visible.



Fig. 10: Wear track of disc PPSA2, after 9000 rounds.

After testing also post mortem images were taken. For instance the worn pin is shown in Fig. 11 the left side on this picture corresponds with the inner diameter of the wear track; right corresponds with the outer diameter of the wear track.

Due to the lighting a curved zone in the middle of the pin can be observed. At the edges of the pin two flat zones are present, with grooves in the direction of motion. The higher middle zone is not right, but follows a certain curvature.

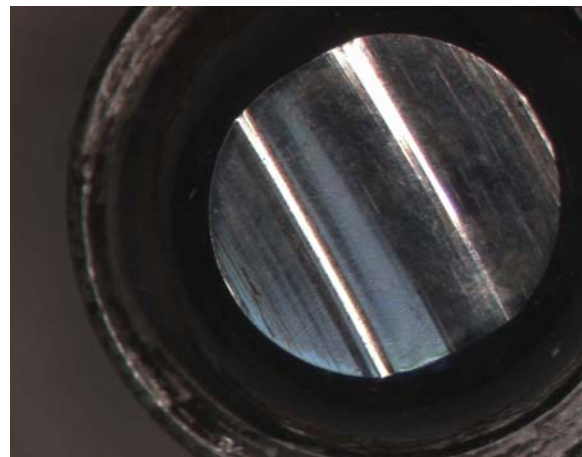


Fig. 11: Resulting contact area of pin after 4 km at 20 mm/s and 250N normal load.

A 3D scan of the worn pin top was taken. The result (see Fig. 12) reveals a zone, which is higher than the two flat zones at the sides.

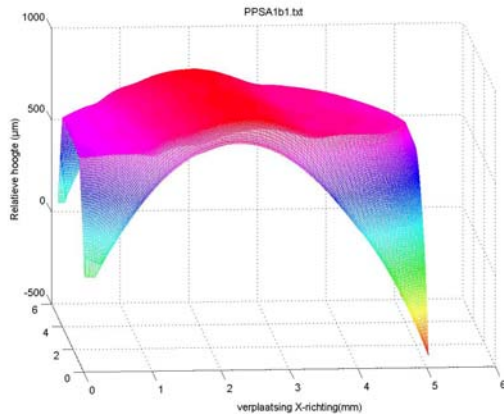


Fig. 12: 3D-scan of final pin top after testing

5. DISCUSSION

The differences between the two tests are due to differences in material structure. Although all the discs had the same stack sequence ($[0^\circ/90^\circ]_{2s}$), a small difference in thickness of the outer PPS layer is possible. The plates for both tests were cut-out from plates made by compression moulding. This technique makes differences in thickness of top layers possible, due to the flow of the thermoplastic polymer, in this case the PPS [15-16]. The difference in thickness of the PPS layer above the first carbon fibres explains the difference in time between Fig. 7 and Fig. 8.

The wear behaviour vs. time can be explained as follows. At the beginning of the test the contact between pin and disc is a point contact, resulting in very high contact pressures. As the top layer of the plate is pure PPS this yields a rather large plastic deformation of the PPS layer. As shown in Fig. 9, break through this PPS layer does not happen at the same time all over the disc. The influence of the orientation of the fibres in the upper fabric, gives an earlier break through for perpendicular orientation to the direction of motion, followed by the parallel orientation, and finally the 45° orientation. This break through could also be visualized when monitoring a full round, where the wear depth changed in relation to the position of the disc. After a completed wear track is formed, carbon starts playing an important role in the friction and wear behaviour.

In the wear track a carbon film is formed. This film lowers the coefficient of friction, (around 75.000 s and 115.000s respectively). But also the formation of this carbon film increases the wear rate of the pin.

The worn pin top, with two flat zones, besides a higher zone in the middle, is due to third body abrasion. Carbon particles, and steel particles after initial wearing of the pin, were pressed outside the wear track. This results in wear debris next to the edges and play a role as third body particles.

The final friction coefficient is around 0.33, which is in agreement to the values found in literature [17-18]. The slight decrease of the friction coefficient in the last part of the test is caused by a decrease of contact pressure with increasing wear (and contact zone).

6. CONCLUSIONS

The following conclusions can be drawn from these tests:

The new test set-up yields promising results and a high repeatability.

The material used in this investigation reveals, in these wear and friction tests, a way to determine differences related to the production process.

The measured friction forces are in relation with values found in literature, and the carbon film created in the wear track decreased the overall friction force.

The wear of the steel pin was, due to the repeatability of the test results, not related to a possible lower quality of the ball at the pin top.

The wear of the pin top is very strongly correlated to the form and the formation of the carbon film into the wear track.

7. ACKNOWLEDGEMENTS

The author W. Van Paepegem gratefully acknowledges his finance through a grant of the Fund for Scientific Research — Flanders (FWO).

The authors also express their gratitude to Ten Cate for their support and technical collaboration.

The authors would like to acknowledge the assistance of Mr. J. Vermeulen for the help rendered in taking SEM pictures Mr. R. Desmet and C. Vermeulen for the help with the development of the test rig, samples and constant advise.

8. REFERENCES

- [1] Z. Hanmin, H. Guoren, Y. Guicheng, Friction and wear of poly-(phenylene sulphide) and its carbon fibre composites. 1. Unlubricated, *Wear* 116 (1987) 59–68.
- [2] Z. Hanmin, H. Guoren, Y. Guicheng, Friction and wear of poly (phenylene sulphide) and its carbon fibre composites. 2. Water lubrication, *Wear* 116 (1987) 69–75.
- [3] B. Bhushan, D.F. Wilcock, Wear behavior of polymetric composites in dry reciprocating sliding, *Wear* 75 (1982) 41–70.
- [4] Y. Laigui, S. Bahadur, An investigation of the transfer film characteristics and the tribological behaviors of polyphenylene sulfide composites in sliding against tool steel, *Wear* 214 (1998) 245–251.
- [5] Q. Zhao, S. Bahadur, A study of the modification of the friction and wear behavior of polyphenylene sulphide by particulate Ag₂S and PbTe fillers, *Wear* 217 (1998) 62–72.
- [6] D.C. Evans, J.K. Lancaster, The wear of polymers, in: D. Scott (Ed.), *Treatise on Material Science and Technology*, Vol. 13, Academic Press, New York, 1979, pp. 85–139.
- [7] C.J. Schwartz, S. Bahadur, Studies on the tribological behavior and transfer film-counterface bond strength for polyphenylene sulfide filled with nanoscale alumina particles, *Wear* 237 (2000) 261–273.
- [8] T.C. Ovaert, S. Ramachandra, Wear particle formation of polymers against smooth hardened steel counterfaces, *Tribol. Trans.* 40 (3) (1997) 445–452.
- [9] Q. Zhao, S. Bahadur, Investigation of the transition state in the wear of polyphenylene sulfide sliding against steel, *Tribol. Lett.* 12 (1)(2002) 23–33.
- [10] C.J. Schwartz, S. Bahadur, Studies on the tribological behavior and transfer film-counterface bond strength for polyphenylene sulfide filled with nanoscale alumina particles, *Wear* 237 (2000) 261–273
- [11] J. P. Davim, N. Marques, Dynamical experimental study of friction and wear behaviour of bovine cancellous bone sliding against a metallic counterface in a water lubricated environment, *Journal of Materials Processing Technology* 152 (2004) 389–394
- [12] K. Friedrich, J. Flöck, K. Váradi, Z. Néder, Experimental and numerical evaluation of the mechanical properties of compacted wear debris layers formed between composite and steel surfaces in sliding contact, *Wear* 251 (2001), pp. 1202–1212
- [13] R.L. Fusaro, Counterface effects on the tribological properties of polyimide composites, *Lubr. Eng.* Vol. 42 (1986), pp. 668–676
- [14] P. Pödra, S. Andersson, Simulating sliding wear with finite element method, *Trib. Int.* 32 (1999), pp. 71–81
- [15] Bigg D, Preston J. Stamping of thermoplastic matrix composites. *Polymer Composites* 1989;10:261±8.
- [16] Karger-Kocsis J. In: Berglund LA, Ericson ML, editors. *Glass mat reinforced polypropylene. Polypropylene: structure, blends and composites*, Vol. 3 ± Composites. ch. 5, London: Chapman & Hall, 1995.
- [17] Y. Yamamoto, M. Hashimoto: Friction and wear of water lubricated PEEK and PPS sliding contacts: Part 2: Composites with carbon or glass fibre, *Wear* 257 (2004), pp. 181–189
- [18] Y. Yamamoto, M. Hashimoto: Friction and wear of water lubricated PEEK and PPS sliding contacts, *Wear* 253 (2002), pp. 820–826